

The Influence of Magnesia Addition and Sintering Temperature on The Properties of Synthesized Electrical Porcelain

Dr. Fadhil A. Chyad

Materials Engineering Department, University of Technology/ Baghdad.

Email: Fchyad_2009@yahoo.de

Fadhaa G. Salem

Education College -Ibn-Al-Haithem, University of Baghdad/ Baghdad

Innam W. Waten

Materials Engineering Department, University of Technology/ Baghdad.

Zahraa F. Attiya

Materials Engineering Department, University of Technology/ Baghdad.

Received on: 30/6/2014 & Accepted on: 4/12/2014

ABSTRACT

The influence of magnesia (MgO) content at different sintering temperatures on the physical and dielectric properties of synthesized electrical porcelain was investigated. Feldspar is one of the major components of porcelain, since feldspar is not available in Iraq, so it was synthesized from Iraqi raw materials. MgO was progressively added in the range (2-30 wt. %) into electrical porcelain. The composed bodies were sintered at temperature in the range (1200-1350 C). Physical properties such bulk density, open porosity beside the Vickers microhardness and dielectric properties such as dielectric constant, loss tangent and dielectric loss factor were measured. The improvement of these properties could associate with an increasing of MgO additive and sintering temperatures. Bulk density, microhardness and dielectric constant are increased with the increasing of MgO content and sintering temperatures. The results reveal that the highest value of density at 30wt. % MgO and at 1350 C for density, hardness and dielectric constant, while it has the lowest value for porosity and loss tangent.

Keywords: Porcelain, Feldspar, MgO, Dielectric constant, Microhardness; loss tangent.

تأثير اضافة المغنيسيا ودرجة حرارة التلبيد على خواص البورسلين الكهربائي المحضر

الخلاصة :

تم دراسة تأثير محتوى المغنيسيا ودرجة حرارة التلبيد على الخواص الفيزيائية والعزلية للبورسلين المحضر . يعتبر الفلدسبار احد المكونات الرئيسية للبورسلين حيث ان هذه المادة غير متوفرة في العراق كمادة اولية . لذا نطلب تصنيعها من مواد محلية لغرض استخدامها في تصنيع البورسلين . ثم اضافة نسب من المغنيسيا ضمن المدى (2%)

-30%) الى البورسيلين المحضر وتليدها ضمن مدى درجات الحرارة (1200-1350) مئوية . تم قياس الخواص الفيزيائية مثل الكثافة والمسامية بالاضافة الى الصلادة والخواص العزلية مثل ثابت العزل وفقدان ظل الزاوية ومعامل الفقدان . تحسنت الكثافة والصلادة وثابت العزل بزيادة نسب المغنيسيا بينما المسامية و فقدان ظل الزاوية انخفضت مع نسب المغنيسيا . كانت نسبة 30% ودرجة حرارة التليد 1350 مئوية هي اعلى النسب للخواص (الكثافة , الصلادة , ثابت العزل) و اقلها للخواص (المسامية وفقدان ظل الزاوية)

INTRODUCTION:

Electrical porcelain has long been used as an electrical insulator in both transmission and distribution lines of electricity. The main properties exhibited by this material are: high mechanical strength, low dielectric loss, superior electrical properties, good creep resistance at room temperature and high corrosion resistance [1]. Triaxial porcelains are primarily composed of clay, feldspar and filler materials, usually quartz or alumina. The clay gives plasticity to the ceramic mixture, quartz maintains the shape of the formed article during firing and feldspar serves as flux.

The three constituents place electrical porcelain in the phase system $[(k, Na)_2O - Al_2O_3 - SiO_2]$ in terms of oxide constituents, hence the term triaxial porcelains [2].

The great interest in high strength of porcelain and the wide research on the porcelain system has resulted in three measure hypothesis which were described by Carty and Sennpati [3] as the mullet hypothesis, the matrix reinforcement hypothesis and the dispersion strengthening hypothesis respectively. According to Morita s' study's replacing some porting of feldspar with Barium Carbonate to prepare porcelain ceramic, the replacement decreases the porcelain centering time[4].

Chaundhuri et. al. studied the mechanical and dielectric strength of porcelain ceramic which have been shown that each phase has its specific influence on these properties depending on its concentration and micro structural attributes[5].

Martin-Marquez et. al. studied the effect of firing temperature on sintering of porcelain .The sintering behavior of fired samples was evaluated by linear shrinkage, water absorption and porosity measurements. Both green powder and fired samples were characterized by means of differential thermal analysis(DTA),XRD,SEM and bending strength measurements[6].

Zahade et al studied the effect of alkaline oxide on the composition of porcelain. Firing shrinking, porosity, density and strength of the samples where studied, all of them were affected by the addition of the alkaline oxide [7].

Sedghi et. al. studied the effect of different fluxes on porcelain insulator properties and structure which has shown that among used fluxes, adding 1% barium carbonate increases the density and bending strength of porcelain [8].

Al – Bermany et. al. studied the influence of ZnO, ZrO₂ and TiO₂ on the mechanical properties of a porcelain body. They found that the addition of these materials made composite good medium for transferring ultrasound waves so they can be used as coated material to enhance the absorption coefficient of porcelain [9].

Olkode et. al. studied the effect of wood ash addition on the properties of porcelain. The flexural strength decreased at the increasing of wood ash content until 5% then the strength improved [10].

Almeida-Junior et. al. investigated the effect of extreme cooling methods on the flexural strength, reliability and shear bond strength of veneer porcelain for zirconia. They found

that fast-cooling method showed a higher flexural strength but a lower reliability in porcelain under tension test configuration, where the slow cooling method decreased the shear bond strength [11].

Sui et al showed that the strength of zirconia-porcelain interface is derived from the mutual diffusion of zirconium and silicon at the interface. Also they found the great Vickers hardness and low toughness suggests the weakness of porcelain [12].

Chyad studied the fracture statistic of porcelain. Two parameters have been used SEM for this study the addition of ZrO_2 powder and effecting of sintering temperature [13].

Sedghi et al prepared six electrical porcelain compositions with different amount of alumina silica and fired at $1300^\circ C$. Density, porosity, bending strength and dialectical strength were measured. Increasing the amount of alumina up to 30% decreases quartz and cristobalite phases but increases corundum phase 3 to 5 times. SEM observation revealed that dense particles and uniform distribution of long and thin needle shaped mullite are predominant in sample microstructure with high dialectical strength [14].

Hariharan et al used Bagasse ash, which is the residue after the sugarcane juice extraction, as a partial replacement of porcelain body. The investigation reveals that high quality ceramic specimens could be achieved from blended material. Thus, sugarcane bagasse ash waste presents high potential for application in the manufacturing of ceramic products. Sample with 20% bagasse ash content resulted in lower porosity, water absorption and high dialectical strength compared to standard porcelain insulator [15].

Vudhivanich et. al. studied the effect of zirconia content on Lucite crystallization and micro structural evaluation of porcelain ceramic –nanocomposite. The amount of ZrO_2 (0-65 wt.%) addition has been found to be one of the keys factors controlling leucite formation and microstructure on the ZrO_2 surface on porcelain ceramic [16].

The employment of feldspar in the composition of ceramics has obvious effect on plasticity, transparency, thermal and mechanical properties. The feldspar plays a very important role in ceramic and glass industry. Substitution of feldspar can be utilized as a replacement. Finally due to the lack of feldspar and its substitutes in Iraq and the imported materials are usually expensive, the feldspar should be synthesized.

The aims of this work are to establish technological roots for the synthesis of feldspar by using locally available materials and then synthesis the porcelain local materials with its characterization.

Experimental Part:

Materials used:

The materials used in this work were Iraqi Duekhla kaolin and Urdhuma sand which brought from Geological Survey Company, the ministry of Industry, Baghdad Iraq. The chemical analysis of these materials was performed at the same company as shown in table(1). The other materials were feldspar and PVA as a binder.

Synthesis of feldspar

Feldspar is not available in Iraq, so it can be synthesis by the following procedure:
-Commercial grade potassium carbonate {98%} was utilized while the other materials were kaolin and silica. The powders were mixed and milled via laboratory milling and sieving system. Powders below 75 micron used for subsequent steps. 20.12wt. % of

K₂CO₃ mixed with 51.3wt. % of kaolin and 26.3wt. % of silica. After good mixing the powder was compacted at 13 MPa to increase the contact area of mixed components and accordingly to enhance solid-solid reaction.

The compacted discs were heat treated up to 1150C for two hours and 10 C/mln. For heating and cooling rate.

Synthesis of Porcelain

50wt% of kaolin, 25wt.% silica and 25wt.% of prepared feldspar were mixed and milled for two hours as mentioned before. 3% of PVA was added to the mixture as a binder. The result powder was compacted as discs (10x10mm) then sintered at (1200, 1250 and 1300 C) for two hours at 10 C/min. as heating and cooling rate.

Characterizations

X-Ray Diffraction

The feldspar powder was analyzed by X-Ray diffraction system type (XRD-6000, Shimadzu-Japan) operated at 35KV and 40mA using Cuka-radiation with wavelength of 1.54056 A.

Physical tests

Bulk density and open porosity of the sintered samples were calculated by the water immersion Archimedes principle by using the related equations [17]:

$$\text{Bulk density} = D / (M - S) \quad \dots(1)$$

$$\text{Open porosity} = (M - D) / (M - S) \times 100 \quad \dots (2)$$

Where:

D is Dry weight (g), M saturated weight (g) and S is the weight of sample after immersing in distilled water and suspended in air through a balance (g).

2.2.3-Hardness test

The Vickers micro hardness was measured according to ASTM E (384-99) using the following equation:

$$H_v = (1.8544P) / d^2 \quad \dots(3)$$

Where, H_v is the Vickers hardness and P is the applied load and d is the indent diagonal. The weight used was 500 g.

Dielectric properties

Dielectric properties such dielectric constant, loss factor and loss tangent have been measured by the HP 4284A precision LCR meter system which used with range of (20Hz-5MHz). The system is computerized results.

Results And Discussion

Fig.1 represents the X-ray diffract gram of synthesized feldspar. This pattern shows sharper peaks and enhanced intensities. The d-spacing values better fit the ASTM

slandered diffraction data files Vol.7 Dec.1997 of feldspar material [18]. The high angle peaks displayed clearly which resembles other indication for good crystallinity for the synthesized feldspar.

Fig. 2 represents the effect of MgO content on the bulk density of electrical porcelain at different temperatures. As shown in this figure as the content of MgO increasing the density is increased and that may be due to the replacement of MgO particles in the main composition of porcelain assuming that the density of MgO is 3.85 g/cm^3 compared to that of porcelain. Also it is clear that the density of the composite increased with the sintering temperature having the highest value with 1350°C , while fig. 3 shows the effect of MgO percentages on the porosity of porcelain at different temperature. The porosity is decreased sharply with the increasing of MgO with sintering temperature that may be due to the filling most of the open pores with MgO particles and making good dense body as seen with the result of density. Fig.4 illustrates the behavior of Vickers' micro hardness of porcelain with different percentages of MgO and different sintering temperature. The figure shows an increasing in the hardness. The highest value at (30%) of MgO and at 1350°C and that may be due to a sufficient fusion for the ceramic body has been occurred which leads to an increase in the glass phase formation that decrease the amount of pores at the surface as shown that at the porosity and density results beside that may be due to the initiation of crystalline phase mullite which has a density of 3.17 g/cm^3 and corundum phase (alumina) which has a density of 3.98 g/cm^3 . The presence of MgO particles in porcelain promote the development of a less viscous liquid phase, which in its turn improves the densification kinetics as long as it is operated within defined liquefied composition and this result agrees with the work of Gıgdemir et. al. (19).

Figs. 5-7 illustrate the effect of MgO content on the dielectric properties such dielectric constant and loss tangent and the dielectric loss factor at different temperatures. Fig. 5 shows that dielectric constant increased with the increasing of MgO content with higher temperature but this increasing is not too much, may be due to the presence of some microcracks in the ceramic insulators, where these cracks are observed mainly near the quartz particles and those regions where the crystalline phase or mullite phase is less or absent. The nature of cracks in porcelain body is depending on the expansion coefficient of the matrix and the particles addition, circumferential cracking than the matrix.

At higher temperature such 1350°C , there will be a considerable amount of glassy phase, when there is a large amount of glassy phase present in the structure, the mobile of ions such as Na^+ , K^+ , Al^{+3} of the matrix and Mg^{+2} of additives finds an easy path to move and hence increases the conductivity. On other hand, the hardness can be greatly increased by undisclosed quartz.

Fig.6 reveals the effect of MgO additive at different temperature on the loss tangent of the samples. As shown in the figure the loss tangent decreased sharply, again the lowest value of the loss tangent was at 1350°C which decreased from 0.016 to 0.0043. The same behavior was for dielectric loss tangent as shown in Fig.7. The dielectric loss tangent decreased drastically specially at the lower MgO additive for all temperatures and then decreased slowly.

Conclusions:

From the experimental results, it was concluding the followings:

- 1- Feldspar can synthesized from locally Iraqi raw materials
- 2- Electrical porcelain can be synthesized from locally Iraqi raw materials.
- 3- Addition of MgO powder enhanced the physical and dielectric properties.
- 4- The higher values of density, hardness and dielectric constant were at 30% MgO and sintering temperature of 1350°C.
- 5- The same percentages of MgO and sintering temperature reduced the porosity and loss tangent to lowest values.

Table (1) chemical analysis of Duekla kaolin and Urduma sand

| Oxides % | Kaolin | sand |
|--------------------------------|--------|------|
| SiO ₂ | 47.26 | 98.4 |
| Al ₂ O ₃ | 34.84 | 0.4 |
| Fe ₂ O ₃ | 1.32 | 0.05 |
| TiO ₂ | 1.4 | -- |
| CaO | 0.15 | 0.3 |
| MgO | 0.38 | 0.3 |
| Na ₂ O | 0.25 | -- |
| K ₂ O | 0.61 | -- |
| L.O.I | 12.91 | 0.55 |
| L.O.I : loss on ignition | | |

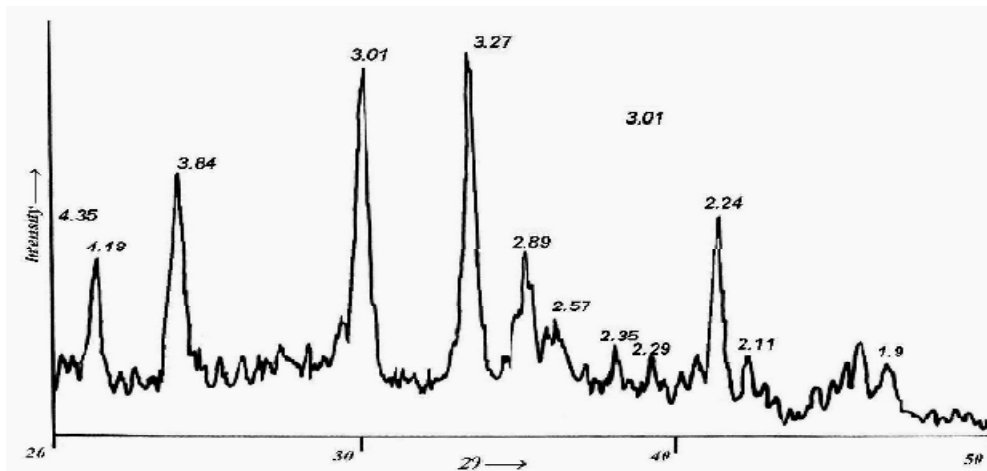


Figure (1) X-ray diffractogram of synthesis of feldspar showing the d – values

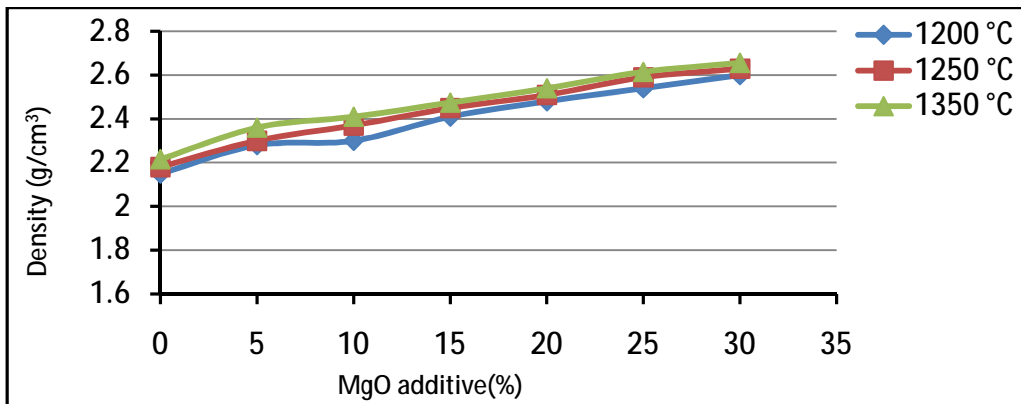


Figure (2) Density of electrical porcelain against MgO additive

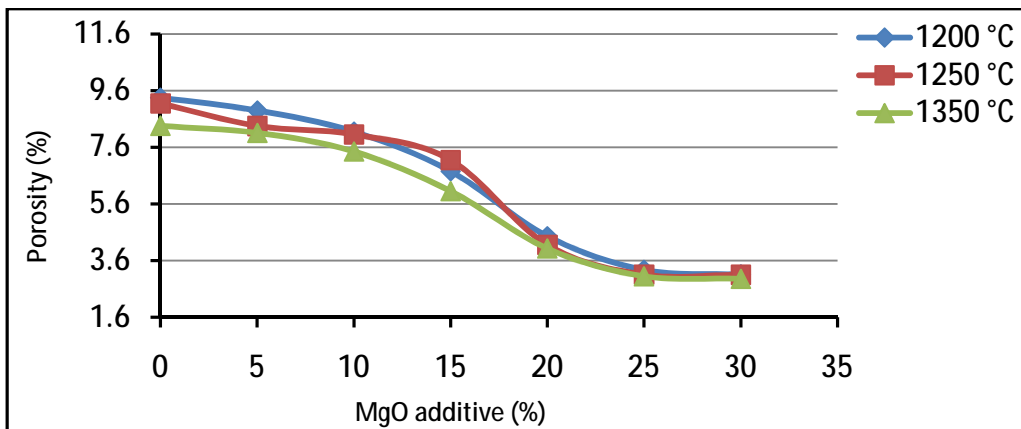


Figure (3) Porosity of electrical porcelain against MgO additive

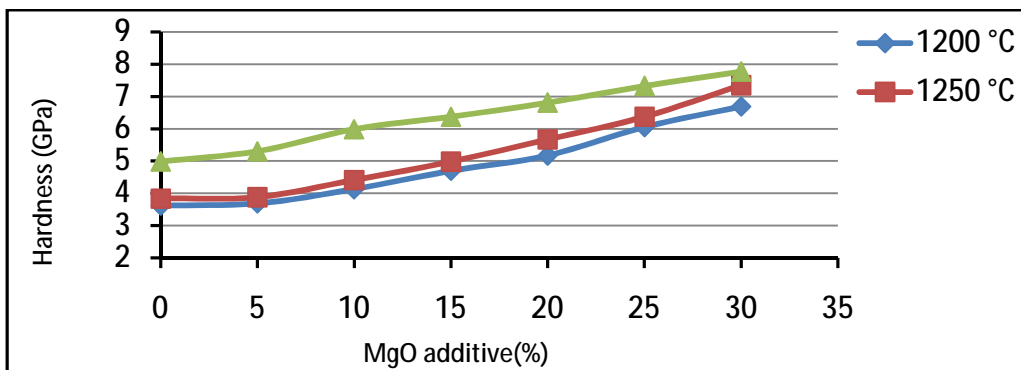


Figure (4) Microhardness of electrical porcelain against MgO additive

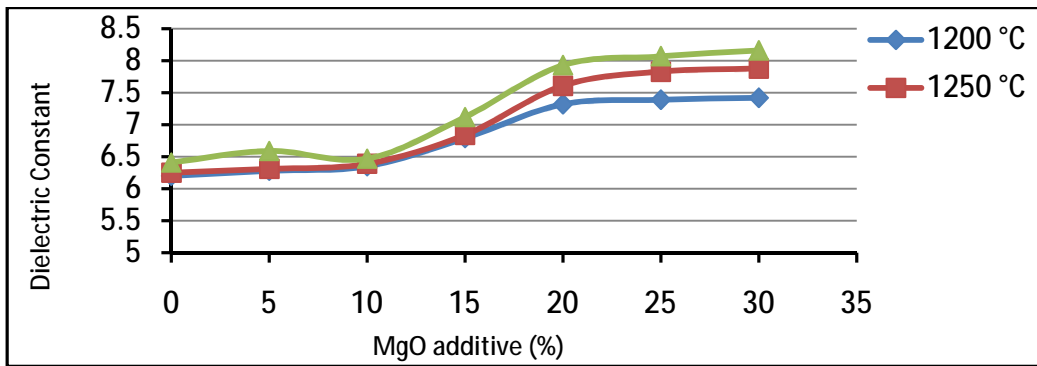


Figure (5) Dielectric constant of electrical porcelain against MgO content at 1MHz


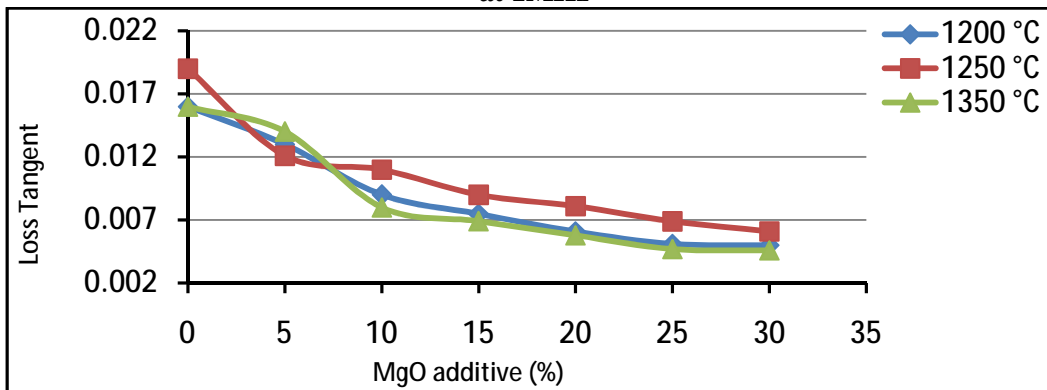


Figure (6) Loss tangent of electrical porcelain against MgO content at different temperature at 1MHz

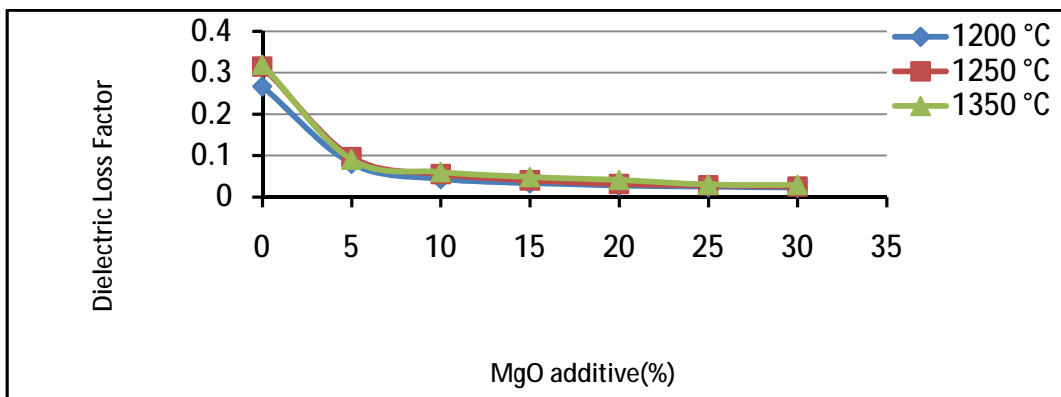

Figure(7) Dielectric loss factor of electrical porcelain against MgO content at 1MHz

References

[1]. J. Lieberman “avoiding quartz in porcelain for high – voltage insulators “. Part J.Am. Ceram. Soci. Bull, vol. 80 pp37-42,2001.

- [2]. R.C.Buchanan “ properties of ceramic insulators “ in ceramic materials for electronics, 2nd ed. R.C. Buchanan,Ed. New York. MarkersDekker Inc. 1991.
- [3]. W.M.Carty and U.Senapati, “ porcelain – rawmaterials processing, phase evaluation and mechanical behavior “ J.Am.Ceram.Soci. 81, pp. 3-20,1998.
- [4]. K. Morita , Y. Suzuki and H. Nozaki , “ Study on electrical strength of suspension insulators in steep impulse voltage range “ IEEE transection on power delivery , Vol. 12 , No. 2 , pp. 128 – 135 , 1997 .
- [5]. S.P. Chandhuri, P. Sarkar and A.K.Churkraborty “ Electrical resistivity of porcelain in relation to constitution “ Ceramic International, 22, pp. 91-99,1999.
- [6]. J. Martin – Marquez , J.M. Rincon and M. Romero , “ Effect of firing temperature on sintering of porcelain “ Ceramic International , 34, pp. 1867 – 1873 , 2008 .
- [7]. Z.B.Ozturk and N.Ay“An investigation of the effect of alkaline oxide on porcelain using factorial design“J. of ceramic processing research,Vol.13,No.2,pp.635– 640, 2012 .
- [8].A. Sedghi, N.Hamidnezhad and N.Riahi Noor, “The effect of fluxes on porcelain insulators properties and structure”, International Conference on Ecological, environmental and biological Sciences (ICEERS) Jan. 7-8, 2012 Dubai.
- [9].A.J.Al-Bermany,F. Hashim and E,Al-Bermany,”Enhancement the mechanical properties of produced porcelain by a ceramic additives using ultrasonic technique”, Chemistry and materials Reaserch,Vol.2,No.6,2012.
- [10].O.S.Okokode,P,O,Alyedun,S.Kuye and B.Anyanwa”Optimization of the wood ash addition on the performance in porcelain” ,The specific J. of Science of technology,Vol,14,No,1,May 2013.
- [11].A.A.Almedia-Junior, D, LonghiniN.Domigues, Santos and G.Adabo”Effect of extreme cooling method on mechanical properties and shear bond strength of bilayered porcelain 3Y-TZP specimens”, J.Of dentistry, Vol.41, pp., 356-362, 2013.
- [12].T.Sui,K.Dragnevsk,T.Neo and A.Korsunsky,”Mechanisms of failure in porcelain-veneered sintered zirconia restoration”13thInternational conference on fracture,June18-21,Beijing,China.2013
- [13].F.A.Chyad,”Fracture statistic of porcelain ceramic:The influence of zirconia additive and sintering temperature”, Eng. &Tech. Journal, Vol.31, No.6 (A), pp.1081-1091, 2013.
- [14].A.Sedghi, N.riahi-Noori, N.Hamidnezhad and M.Salmani”Effect of chemical composition and alumina content on structure and properties of ceramic insulators”, Bull. Mater.Sc. Vol.37, N0.2, April, pp321-325, 2014.
- [15].V.Hariharan, M.Shanmugam, K.Amutha and G.Sivakumar,”Preparation and characterization of ceramic product using sugarcane Bagasse ash waste”, Research Journal Recon Sciences, Vol.3, PP.6770, 2014.
- [16].N.Vudhivanich, A.Pisitanusorn and S. Anata,”Effect of zirconia content on leucite crystallization and microstructure evolution of porcelain ceramic-nanocomposites”, Chiang Mat.J.Sce. Vol.14 No.2 pp.435-446, 2014.
- [17].ASTM Designation, C-373-77”Water absorption, apparent density, and apparent porosity of fired products”1977.
- [18].W.F,McCune,”ASTM Powder diffraction powder file”Internatioal center for diffraction data,puplished by the JCPDS,USA,Vol.7,1997.
- [19].G.Cigdemir, A.Kara, and F Kan, International Ceramic, Vol.30, pp.171-186, 2010.